



Intermetallic Phase Precipitation in Duplex Stainless Steels: Considerations on the Use of Johnson-Mehl-Avrami-Kolmogorov Equation

Paolo Ferro^{1*}, Alberto Fabrizi¹ and Jan-Olof Nilsson²

Abstract

Despite the great interest in intermetallic phase precipitation in duplex and super duplex stainless steels, a common controlling factor in the kinetics of its formation has not been reached yet. For example, when the time-evolution of sigma phase precipitation is described by the Johnson-Mehl-Avrami-Kolmogorov (JMAK) equation, or its modified forms, very different kinetic parameters were found in the literature, even if duplex stainless steels with very similar chemical composition and initial conditions are used in the experiments. In this work, some critical points that affect the evaluation of the kinetic constants and may cause erroneous interpretation of intermetallic phase precipitation (kinetics) are highlighted and discussed. It was shown that the choice of a high impingement coefficient in the modified JMAK equation leads to a significant improvement in experimental data description. A series of recommendations for the future application of the JMAK equation applied to intermetallic phase precipitation in duplex stainless steels are finally suggested.

Keywords

Duplex stainless steel; Sigma phase; Precipitation; Kinetics; Modeling

Introduction

A great number of studies have been conducted on the kinetics and microstructural evolution of intermetallic phases in duplex and superduplex stainless steels (DSS, SDSS) since their presence significantly influences the mechanical properties and corrosion resistance of the mechanical components. With particular attention to σ phase, many authors have tried to assess the kinetic precipitation mechanism from the volume fraction variation as a function of time [1-8]. In those works, isothermal σ phase time-evolution was generally described by the Johnson-Mehl-Avrami-Kolmogorov (JMAK) equation, which is formulated in the original paper by Avrami [9] as follows:

$$1 - V = \exp[-Bt^k] \quad (1)$$

Where, V is the fraction transformed at time t , B is a function of temperature and k is a constant varying between 1 and 4 and

depending upon the nucleation and growth mechanism. Since then, many workers commonly write Eq. (1) as:

$$f = \frac{V}{V_{eq}} = 1 - \exp[-Kt^n] \quad (2)$$

where V_{eq} is the equilibrium amount of transformed phase at temperature T , K is an overall rate constant and n is the Avrami exponent. This equation is universal if the assumed conditions in the model are not violated. However, such conditions are seldom obtained experimentally. In the JMAK model, the transformation is supposed to occur in an infinite medium and initiate by homogeneous nucleation with nuclei having a negligible initial radius. Nuclei grow isotropically at a constant rate and their growth stops at points of impingement whereas it continues unabated elsewhere. Theoretically, the JMAK equation can be applied in the case of continuous nucleation or site saturation, and for volume diffusion controlled growth or interface controlled growth. The model cannot be derived for a mixture of the nucleation models [10]. However, when the kinetics parameters are calculated with JMAK-like equations, the values of the JMAK exponent are very often between the expected values for site saturation and continuous nucleation [10].

In order to extrapolate the kinetic parameters (n, K) from experimental data, Eq. (2) is often rearranged as follows:

$$\ln \left[\ln \left(\frac{1}{1-f} \right) \right] = \ln K + n \cdot \ln t \quad (3)$$

The phase transformation kinetics obeys the classical JMAK model when the evolution of $\ln[\ln(1/(1-f))]$ as a function of $\ln(t)$ gives a straight line (Avrami plot).

When studying intermetallic phase precipitation, different authors [4,7,8] have found that a better interpolation of the experimental results is obtained by using a modified JMAK model [11]:

$$f = 1 - \left[\frac{1}{1 + c(Kt)^n} \right]^{1/c} \quad \text{with } c \neq 0 \quad (4)$$

where c (coefficient) is the impingement exponent used to correct some complex competing effects that may occur during precipitation such as: a) depletion of the solute content in the untransformed matrix due to competitive growth of the fraction products, b) direct collision of two advancing reaction products, or c) exhaustion of nucleation sites.

In addition to the theoretical restrictions of the JMAK model, there are also physical phenomena to take into account. Kinetic parameters of intermetallic phase precipitation are influenced by chemical composition [12], solution heat treatment [13] (and consequently primary phase proportion, phase and grain size), hot and cold working [14,15], as well as aging time and temperature. Although the analysis in the present paper refers to alloys within the specification of 2205 it is quite apparent that there are significant individual variations that cannot be ignored (Table 1). For instance, the alloy with the highest chromium content (22.87%) also exhibits the highest content of molybdenum (3.21%). Because both of these elements promote sigma-phase formation this particular alloy [8] is expected to be the one that is most unstable microstructurally. It is not surprising that very different JMAK kinetic parameters were

*Corresponding author: Paolo Ferro, Department of Engineering and Management, University of Padova, Stradella San Nicola 3, 36100 Vicenza, Italy, Tel: +39 0444 998769; Fax: +39 0444 998888; E-mail: ferro@gest.unipd.it

Received: April 03, 2017 Accepted: April 20, 2017 Published: April 25, 2017

Table 1: Kinetic parameters related to sigma phase precipitation in a DSS 2205.

Authors	Chemical composition (wt%) of DSS 2205								T_e	$T_s(^{\circ}\text{C}), t_s$ (min), (V δ /V γ)	$T_a(^{\circ}\text{C})$	$T_n(^{\circ}\text{C})$	V_{eq}	n	c	Q (KJ/mol)	Controlling factor in the formation of sigma phase
	Cr	Ni	Mo	N	Mn	Si	C	Cu									
Elmer et al. [1]	22.43	4.88	3.13	0.18	0.14	0.67	0.023	-	860**	1065,-,(54:46)	850	800	24*	7÷ 0.73	0	375÷466	Nucleation
Radji et al. [4]	22.65	5.01	2.19	0.13	1.21	0.29	0.03	0.21	-	1050,-,(51:49)	850	-	-	1.4	0.3	98.91	Diffusion (interface reaction)
Magnabosco [3]	22.2	5.70	2.98	0.16	1.6	0.44	0.016	-	940**	1120,30,(41:59)	850	850	>54	1	0	185	Grain Boundary Cr diffusion
Ferro and Bonollo [2]	22.87	5.11	3.21	0.17	1.55	0.43	0.02	0.38	915	1050,30,(56:44)	850	868	25	0.97	0	-	Site Saturation
Lara et al. [5]	-	-	-	-	-	-	-	-	-	-	800	-	-	0.77	0	-	-
Momeni and Deghani [14]	21.23	6.55	3.03	-	0.024	0.87	0.02	-	-	1150,20,(47:53)	800	-	25	1	0	-	Site Saturation
Calliari et al. [26]	22.75	5.04	3.19	0.16	1.46	0.56	0.03	-	-	1050,30,(49:51)	850	-	25	4.11	0	-	Grain Boundary diffusion
Sieurin and Sandstorm [30]	21.46	5.5	2.98	0.16	1.46	-	-	-	930**	-	-	865	-	-	-	-	Diffusion of Mo
Calucio Dos Santos and Mafnabosco [32]	22.07	5.68	3.20	0.17	1.38	0.34	0.017	0.15	960**	1175,30, (57:43)	850	850	~28%	1.42;0.22	0	341;24	Diffusion of Mo (σ nucleation)

Note: *Estimated value, **ThermoCalc; T_e =solvus temperature; T_s =solution temperature; t_s = solution holding time; V_{δ}/V_{γ} , primary phases balance; T_a = aging temperature; T_n =temperature at the nose of the C curve; V_{eq} =equilibrium amount of transformed sigma phase at T_a ; n =Avrami exponent; c =impingement exponent; Q =activation energy

found. For the above-mentioned reasons, a universal master model describing intermetallic phase precipitation is hardly deduced from literature data. Table 1 summarises the results obtained by different authors about the kinetics of sigma phase precipitation in a DSS 2205 starting from very similar initial conditions and aging temperatures of 1073 K (800°C) or 1123 K (850°C). Obviously, very different values of the Avrami time exponent were obtained.

Other than theoretical and physical aspects, such anomalies may be due to uncertainties in the experimental data or to an incorrect use of the model as well. The first ones are associated with the experimental procedure (i.e.: difficulties in obtaining a rapid heating to the aging temperature or errors associated with intermetallic phase quantification methodology (e.g. Optical Microscope (OM), Scanning Electron Microscope (SEM), thermoelectric power [5], Electron Backscatter Diffraction (EBSD)). The incorrect use of the model may be related to the violated conditions of validity [16-20] as well as the inappropriate choice of the kinetic model (i.e.: Eq. (2) instead of Eq. (4)) [21] or an erroneous formulation of the model itself [22].

In this paper the possible causes of these anomalies are highlighted and a series of recommendations for the future application of the JMAK equation to intermetallic phase precipitation in DSS and SDSS are suggested. Some of these recommendations are already mentioned in the literature, others have not yet been taken into account. The aim of this work is to collect in a single paper the main critical issues related to the use of the JMAK equation in order to improve, in the future, the experimental data interpretation with particular attention to secondary phase precipitation in DSS and SDSS. As an example, in the final part of the paper it is shown that, by using an appropriate model for σ phase precipitation and experimental data taken from the work of Elmer et al. [1], the value of the Avrami coefficient (n) can be reinterpreted (compared to the conclusions deduced by Elmer et al. [1]) and found more in agreement with the theoretical values ($n=1\div 4$).

Theoretical Analysis

When the kinetics of intermetallic phase precipitation is studied in the frame of the JMAK theory or its modifications, the kinetic parameters are obtained by interpolating experimental results ($f(t)$) with Eq. (3) or its modified forms [4]. In the following paragraphs each parameter of the JMAK equation is analysed and discussed. All experimental data with particular reference to the kinetics of sigma phase precipitation in DSS 2205 are taken from literature.

Equilibrium amount of transformed phase at temperature T (V_{eq})

The use of Eq. (3) requires knowledge of the equilibrium amount of transformed phase at temperature T (V_{eq}) and the time needed to reach it (Eqs. (2) and (3)). However, such parameters are often uncertain. First of all it is not always explicitly mentioned whether the equilibrium fraction of sigma-phase is that defined by the composition of ferrite or the overall composition. If the austenitic phase is not included in the calculations, the redistribution of nitrogen, which is very fast, is neglected. Although the role of nitrogen has not been investigated in detail it is highly likely that it plays an important role in the formation of sigma-phase.

The V_{eq} value depends significantly on chemical composition of the alloy [12] and temperature. At temperature $T=1123$ K (850°C), thermodynamic calculations by means of Thermo-Calc® (TCFE8 database), give a value of $V_{eq} \approx 24$ pct. (against a value of 30 pct. obtained after 360 h of aging [31]). Previous calculation of the phase equilibria showed a value of V_{eq} (1123 K (850°C)) ≈ 20 pct by using an earlier and a different version of ThermoCalc [1,3]. Even when such a parameter (V_{eq}) is obtained by means of experimental tests, the measured values differ from thermodynamic calculations and from each other. For example, Magnabosco [3] obtained a value of V_{eq} (1123 K (850°C)) ≈ 54 pct. He suggested that equilibrium was not reached at the studied temperatures even considering the long-

term aging applied. Other researchers found values of about 25 pct (Table 1) by relative short-term aging (~10 h) and by a not specified estimation method [1]. Theoretically, by using the Avrami plot (Eq.3) and data of intermetallic phase volume fraction obtained by short-term aging, it would be possible to extrapolate the value of V_{eq} and the time needed to reach it. However it is not always possible to use such a methodology because data do not always follow the linear trend of the Avrami plot [1,4]. In those cases, the impingement exponent c should be known *a priori*.

Some uncertainties about the value of V_{eq} may depend on the methodology of investigation used (i.e.: SEM, EBSD, standard metallography) [23]. In particular, uncertainties on intermetallic phase quantification are strongly reduced if Z contrast mode-SEM (Z=atomic number) or EBSD techniques are used instead of standard metallography (image analysis applied to optical micrographs) [24-26]. If the corrosion products of the etchant enhance the contours, the image analysis overestimates the areas; while, if the intermetallic phase is not completely etched, image analysis underestimates the corresponding areas. Similar effects were observed when analysing sigma-phase in an austenitic stainless steel of type 347 [27] and is equally applicable in duplex stainless steels. In the present work, by using ten SEM micrographs at 1000X on unetched samples processed by ImageJ software, it was found that after 27 h at 1123 K (850°C) the sigma transformation is not yet completed (Figure 1); after 504 h ferrite completely disappeared and a value of V equal to 27.8 ± 0.5 pct. was obtained (DSS 2205 chemical composition: Cr 22.56, Ni 5.32, Mn 0.84, Mo 2.9, C 0.029, Si 0.34, Fe Bal. (wt%)). It can be observed that this value is close to the standard value assumed in the literature (25 pct., Tab. 1) and that was obtained after long-term aging [3]. From the above considerations it can be understood that a common value of $V_{eq}(T)$ has not yet been reached. Even if slight variations in alloy chemical composition may result in a high variation in the V_{eq} value, further investigations and theoretical consideration seem necessary to obtain coherent and realistic values of such a parameter as a function of temperature.

The rate constant (K) and the activation energy (Q)

In the literature, the JMAK equation is used by some authors [2,3,5,6,14] in its original form (Eq. (2)) [9] and by others authors [1,4,7] in the following form:

$$f = 1 - \exp[-(Kt)^n] \quad (5)$$

where it can be noted that now K is squared to n and thus Eq. (3) becomes:

$$\ln \left[\ln \left(\frac{1}{1-f} \right) \right] = n \cdot \ln K + n \cdot \ln t \quad (6)$$

At constant temperature, if it is assumed that the Avrami exponent n does not vary in time, n and K are constants. Consequently, the interpolation of experimental data with Eq. (3) or (6) does not affect the value of n ; however, by using alternatively Eq. (3) or (6), different values of K are expected. In particular, the values obtained will differ by a constant. This could result in an error if the constant K is used to calculate the activation energy (Q) of the precipitation process by the following equation:

$$K = K_0 \exp(-Q/RT) \quad (7)$$

where K_0 is the pre-exponential factor, Q is the activation energy and R is the gas constant.

The use of an Arrhenius-like temperature dependence for the rate constant has been assumed several times [1,3,4], without motivation. Since the values of K were calculated with both Eq. (3) and Eq. (6), errors in the calculation of Q and erroneous interpretations of the precipitation mechanism of intermetallic phase are present in literature. In a recent work on σ phase dissolution in a DSS 2205 [28], it was found that if the activation energy was calculated by assuming the dependence of K by the exponent n , the activation energy value for σ phase dissolution was very close to the activation energy of Cr grain boundary diffusion; otherwise, the calculated values was an order of magnitude higher than the previous one and thus without physical significance. Consequently, it seems reasonable that the correct value of K is obtained by using Eq. (5) instead of Eq. (2).

Furthermore, it should be recognised that, in the case of intermetallic phase precipitation, the use of an Arrhenius-like temperature dependence for the rate constant is problematic if the undercooling is small. The rate of nucleation (\dot{N}_{het}) of sigma particles is given by:

$$\dot{N}_{het} = \nu N_v \exp\left(-\frac{\Delta G_{het}^*}{RT}\right) \exp\left(-\frac{Q_d}{RT}\right) \quad (8)$$

where ν is a vibration frequency factor, N_v is the total number of heterogeneous nucleation sites per unit volume, ΔG_{het}^* is the energy barrier against nucleation and Q_d is the activation energy for the

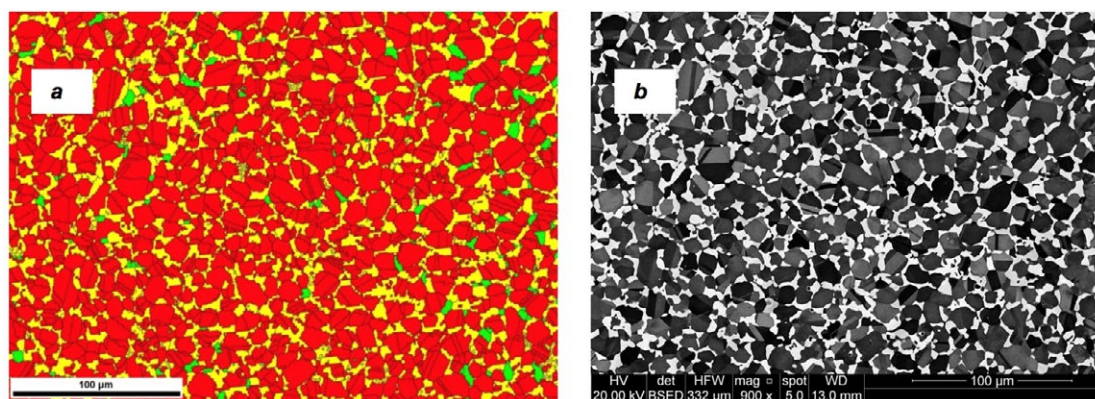


Figure 1: Micrographs of 72h-aged 2205 DSS sample: a) EBSD phase map: sigma (yellow), austenite (red), ferrite (green); b) BSE-SEM micrograph: sigma (white); after polishing with colloidal silica, twins within γ -austenite grains can be seen.

atomic migration across the nucleus/matrix interface. Now, \dot{N}_{het} can be approximated as $A/\Delta T^2$ [10], where A is a constant and ΔT is the undercooling or overheating with respect to the temperature at which the two phases are in equilibrium. Conversely to intermetallic phase dissolution, during intermetallic phase precipitation the nucleation rate \dot{N}_{het} is highest at an intermediate temperature (due to the competitive influence of undercooling (driving force) and diffusivity on the reaction kinetics) (Figure 2).

It means that the characteristic C-shape of time-temperature-transformation (TTT) curves for precipitation cannot be modelled by substituting Eq. (7) in Eq. (5). Despite this, different authors used Eq. (7) for the calculation of Q without specifying the limits of applicability of that formula [3,4].

Now, if it is supposed that during the early stage of intermetallic phase precipitation, the reaction rate is controlled by the nucleation rate (\dot{N}_{het}), the time taken to precipitate a certain fraction of intermetallic phase (t^*) is inversely proportional to \dot{N}_{het} [29]:

$$t^* = \frac{b}{N_v} \exp\left(\frac{\Delta G_{het}^*}{RT} + \frac{Q_d}{RT}\right) \quad (9)$$

where b is a kinetic constant. By taking the natural logarithm on both sides of Eq. (9), the following equation is obtained [29]:

$$\ln(t^*) = \ln\left(\frac{b}{N_v}\right) + \frac{\Delta G_{het}^* + Q_d}{RT} \quad (10)$$

By plotting $\ln(t^*)$ vs $1/T$, a C-curve is obtained with well-defined asymptotes. At high undercooling, ΔG_{het}^* is negligible and the slope of the curve becomes constant and equal to Q_d/R . Starting from the experimental C-curve, it is thus possible to calculate Q_d . By using this method, Elmer et al. [1] calculated values of Q_d for σ phase precipitation significantly higher than the activation energy for Cr and Mo diffusion as obtained by others authors [3,30]. They concluded that nucleation is likely a controlling factor in the formation of sigma. This is consistent with the observation that there is no well-defined orientation relationship between sigma and the ferritic matrix [31] and the fact that chi-phase, which is isomorphous with the matrix and therefore nucleates much more easily, often provides necessary nucleation sites for sigma-phase. It should be added that the ability to form chi-phase is a strong function of the composition, a circumstance that complicates comparisons even further. However, this method could be dependent on the number of discrete experimental points used to model the shape of the C-curve. As a matter of fact, the asymptote slope may vary accordingly.

Most experimental work of this kind has been performed by cooling down to room temperature before the ageing treatment. Because of the experimental limitations rather few investigations have employed ageing immediately after solution treatment, thereby avoiding cooling and subsequent heating. The former situation builds up more nuclei and, therefore, enhances the kinetics. This circumstance also leads to difficulties when comparing results from different sources.

The time exponent (n) and the impingement exponent (c)

Despite the use of DSS 2205 samples with similar composition and microstructure (prior to the ageing heat treatment), different values of the Avrami exponent were obtained in the literature (Table 1). This is partly due to the dependence of n on many parameters related to the initial conditions of the material (i.e.: austenitic/ferritic grain size, solution time and temperature); partly to the difficulties inherent

in the isothermal test execution. For example, the time to reach the isothermal temperature is critical and the use of small samples and salt bath is therefore crucial. *De facto*, the Avrami exponent calculation by using Eq. (5) and data obtained with short aging heat treatments may be significantly influenced by the experimental methodology used.

About sigma phase precipitation, the Avrami coefficient was found both constant [2-4] and variable during the isothermal aging [1,32]. In this last case, it was suggested that the variation of the local Avrami coefficient $n(f)$ is due to a change in the transformation mechanism. However, as observed by Wang et al. [21], a changing kinetic exponent may result from inappropriate use of kinetic model. At $T=1123$ K (850°C), Elmer et al. [1] found that the local Avrami exponent varies from 0.7 to 7 (Figure 3a). They thus suggested that the mechanism for the transformation is changing as the transformation proceeds. However, by means of Eq. (4), it is easy to verify how it is possible to linearize the experimental results by Elmer et al. [1] in a plot $\ln(((1-f)^{-c}-1/c))$ versus $\ln(t)$. The values of n (≈ 4) were found to have only a slight dependence on temperature (Figure 3b).

In order to linearize the experimental results by Elmer et al. [1], high values of the impingement coefficient c were found in this work compared to those found in literature about sigma phase precipitation ($c=10$ against $c=0.3$ [4]). It is however clear that the experimental results by Elmer et al. [1] are very different from those obtained by other authors in literature (Table 1) and deeper investigations may be necessary for a better comprehension of σ phase precipitation kinetics.

From the above observations, the following generalised JMAK model is thus suggested:

$$f = \begin{cases} 1 - \exp[-(Kt)^n] & \text{with } c = 0 \\ 1 - \left[\frac{1}{1 + c(Kt)^n}\right]^{1/c} & \text{with } c \neq 0 \end{cases} \quad (11)$$

Conclusions

Intermetallic phase precipitation in DSS 2205 is influenced by many factors such as the initial alloy conditions, e.g. austenitic/

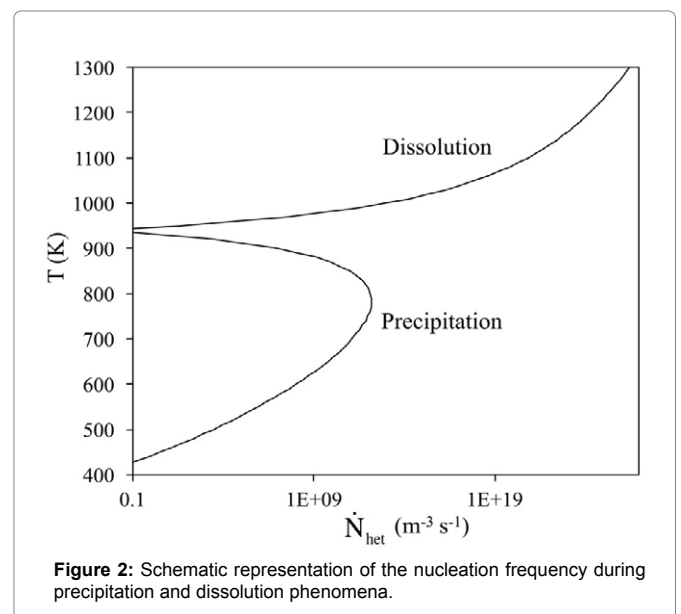


Figure 2: Schematic representation of the nucleation frequency during precipitation and dissolution phenomena.

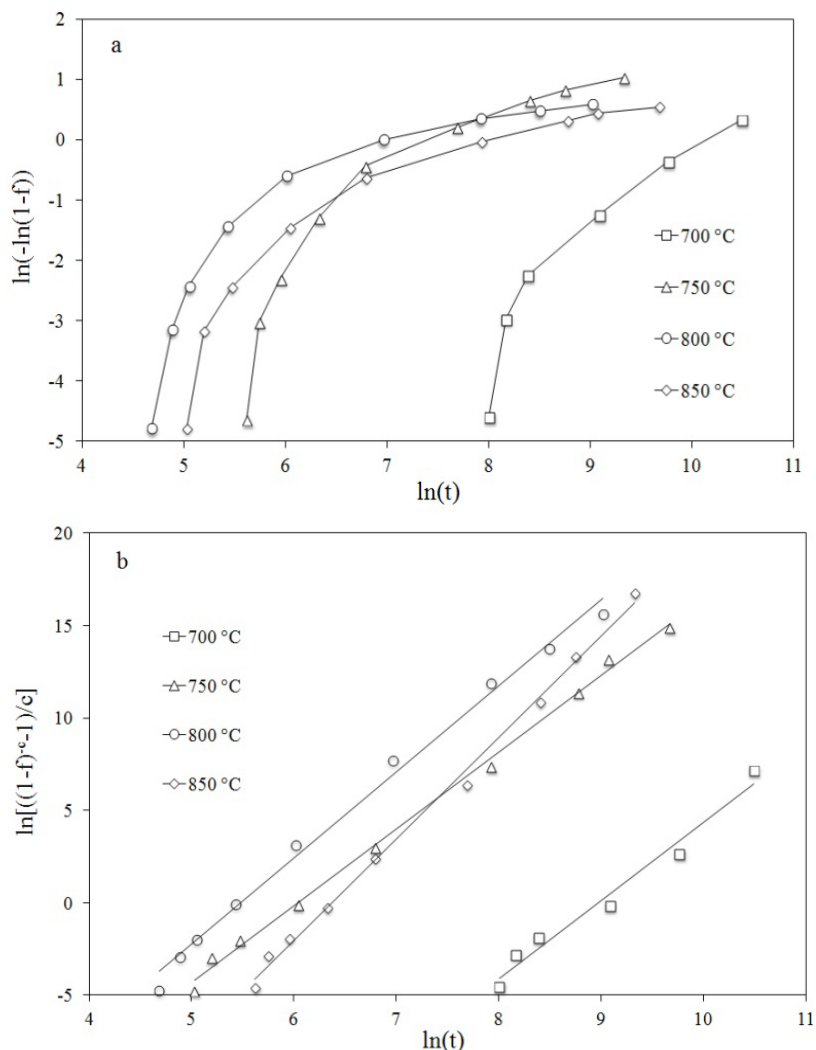


Figure 3: JMAK plot of the sigma phase fraction: a) from JMAK equation ($c=0$) [1], b) from modified JMAK equation ($c=6.75$, ($T=973-1023$ K (700-750°C)), $c=10$ ($T=1073-1123$ K (800-850°C)), $n(700^\circ\text{C})=4.23$, $n(1023$ K (750°C))=5.5, $n(1073$ K (800°C))=4.65, $n(1123$ K (850°C))=4.15).

ferritic grain size, primary phases balance, ageing temperature and heterogeneous nuclei distribution. For this reason it seems unlikely that a universal master model on the formation of intermetallic phase can be achieved. However, when the kinetic mechanism of intermetallic phase precipitation is assessed by means of the JMAK equation, some recommendations are suggested in order to correctly interpret the experimental results:

With particular reference to σ phase, the equilibrium amount of transformed phase at temperature T (V_{eq}) should be obtained by very long aging heat treatments.

The general formulation of JMAK equation should be used (Eq. (11)).

When the rate constant K is used to calculate the activation energy (Q), it should be squared to n in the JMAK formulation.

In case of sigma phase precipitation, the activation energy should be calculated by using only experimental data at sufficiently low temperatures.

The amount of intermetallic phase, if calculated by means of image analysis, should be obtained by using EBSD or SEM micrographs of unetched samples.

The use of small samples and salt bath is recommended in order to reduce the time to reach the isothermal temperature, especially when volume fractions of intermetallic phase at short aging times have to be measured.

References

1. Elmer JW, Palmer TA, Specht ED (2007) Direct observations of sigma phase formation in duplex stainless steels using in-situ synchrotron x-ray diffraction. Metall Mater Trans A 38: 464-475.
2. Ferro P, Bonollo F (2012) A semiempirical model for sigma-phase precipitation in duplex and superduplex stainless steels. Metall Mater Trans A 43: 1109-1116.
3. Magnabosco R (2014) Kinetics of sigma phase formation in a duplex stainless steel. Mat Res 12: 321-327.
4. Badji R, Kherrouba N, Mehdi B, Cheniti B, Bouabdallah M, et al. (2014) Precipitation kinetics and mechanical behavior in a solution treated and aged dual phase stainless steel. Mater Chem Phys 148: 664-672.

5. Lara NO, Ruiz A, Rubio C, Ambriz RR, Medina A (2011) Nondestructive assessing of the aging effects in 2205 duplex stainless steel using thermoelectric power. *NDT&E International* 44: 463-468.
6. Wilson A, Nilsson JO (1996) Modelling the CCT-diagram of intermetallic phase precipitation in duplex stainless steels from isothermal experiments. *Scand J Metall* 25: 178-185.
7. Badji R, Bouabdallah M, Bacroix B, Kahloun C, Bettahar K, et al. (2008) Effect of solution treatment temperature on the precipitation kinetic of σ -phase in 2205 duplex stainless steel welds. *Mater Sci Eng* 496: 447-454.
8. Ferro P, Bonollo F, Timelli G (2012) Sigma phase precipitation modelling in a UNS S32760 superduplex stainless steel. *Metall Ital* 5: 7-12.
9. Avrami MJ (1939) Kinetics of phase change. I general theory. *Chem Phys* 7: 1103.
10. Kempen ATW, Sommer F, Mittemeijer EJ (2002) Determination and interpretation of isothermal and non-isothermal transformation kinetics: the effective activation energies in terms of nucleation and growth. *J Mater Sci* 37: 1321-1332.
11. Lee ES, Kim YG (1990) A transformation kinetic model and its application to Cu-Zn-Al shape memory alloys-I. Isothermal conditions. *Acta metal Mater* 38: 1669-1676.
12. Huang CS, Shih CC (2005) Effects of nitrogen and high temperature aging on σ phase precipitation of duplex stainless steel. *Mater Sci Eng* 402: 66-75.
13. Kashiwar A, Vennela NP, Kamath SL, Khatirkar RK (2012) Effect of solution annealing temperature on precipitation in 2205 duplex stainless steel. *Mater Charact* 74: 55-63.
14. Momeni A, Dehghani K (2010) Effect of Hot Working on Secondary Phase Formation in 2205 Duplex Stainless Steel. *J Mater Sci Technol* 26: 851-857.
15. Cho HS, Lee K (2013) Effect of cold working and isothermal aging on the precipitation of sigma phase in 2205 duplex stainless steel. *Mater Charact* 75: 29-34.
16. Liu F, Yang CL, Yang GC, Li JS (2007) Deviations from the classical Johnson-Mehl-Avrami kinetics. *J Alloy Compd* 560: 326-330.
17. Liu F, Yang G (2007) Effects of anisotropic growth on the deviations from Johnson-Mehl-Avrami kinetics. *Acta Mater* 55: 1629-1639.
18. Levine LE, Narayan KL, Kelton KF (1997) Finite size corrections for the Johnson-Mehl-Avrami-Kolmogorov equation. *J Mater Res* 12: 124-132.
19. Sun NX, Liu XD, Lu K (1996) An explanation to the anomalous Avrami exponent. *Scripta Mater* 34: 1201-1207.
20. Todinov MT (2000) On some limitation of the Johnson-Mehl-Avrami-Kolmogorov equation. *Acta Mater* 48: 4217-4224.
21. Wang J, Kou HC, Gu XF, Li JS, Xing LQ, et al. (2009) On discussion of the applicability of local Avrami exponent: errors and solutions. *Mater Lett* 63: 1153-1155.
22. Khanna YP, Taylor TJ (1988) Comments and recommendation on the use of the Avrami equation for physico-chemical kinetics. *Polym Eng Sci* 28: 1042-1045.
23. Michalska J, Chmiela B (2014) Phase analysis in duplex stainless steel: comparison of EBSD and quantitative metallography methods. *Mater Sci Eng* 55: 1-9.
24. Breda M, Pellizzari M, Frigo M. (2015) σ -Phase in lean duplex stainless steel sheets sin. *Acta Metall* 28: 331-337.
25. Ferro P, Fabrizi A, Bonollo F (2016) Non-isothermal dissolution modelling of sigma phase in duplex stainless steels. *Acta Metall* 29: 859.
26. Calliari I, Zanesco M, Ramous E (2006) Influence of isothermal aging on secondary precipitation and toughness of a duplex stainless steel SAF 2205. *J Mater Sci* 41: 7642-7649.
27. Erneman J, Nylöf L, Andrén HO, Nilsson JO (2004) Quantitative metallography of sigma phase precipitates in AISI 347 stainless steel: a comparison between different methods. *Mater Sci Techn* 20: 1245-1251.
28. Ferro P (2013) A dissolution kinetics model and its application to duplex stainless steels. *Acta Mater* 61: 3141-3147.
29. O. Grong (1994) Metallurgical modeling of welding. The Institute of Materials, London.
30. Sieurin H, Sandström R (2007) Sigma phase precipitation in duplex stainless steel 2205. *Mater Sci Eng* 444: 271-276.
31. Gregori A, Nilsson JO (2002) Decomposition of ferrite in commercial superduplex stainless steel weld metals: microstructural transformations above 700°C. *Metall Mat Trans A* 33A: 1009-1018.
32. Dos Santos DC, Magnabosco R (2016) Kinetic study to predict sigma phase formation in duplex stainless steels. *Metall Mat Trans A* 47: 1554-1565.

Author Affiliation

Top

¹Department of Engineering and Management, University of Padova, Stradella San Nicola 3, 36100 Vicenza, Italy

²JON Materials Consulting, N. Hasselgatan 11, 811 35, Sandviken, Sweden

Submit your next manuscript and get advantages of SciTechnol submissions

- ❖ 80 Journals
- ❖ 21 Day rapid review process
- ❖ 3000 Editorial team
- ❖ 5 Million readers
- ❖ More than 5000 
- ❖ Quality and quick review processing through Editorial Manager System

Submit your next manuscript at • www.scitechnol.com/submission